



DISCLAIMER: The use of this standard is governed by the "Texas Engineering Practice Act". No warranty of any kind is made by TxDOT for any purpose or for any use. TxDOT assumes no responsibility for the conversion of this standard to other formats or for incorrect results or damages resulting from its use.

DATE: FILE:

FULL DEPTH REPAIR

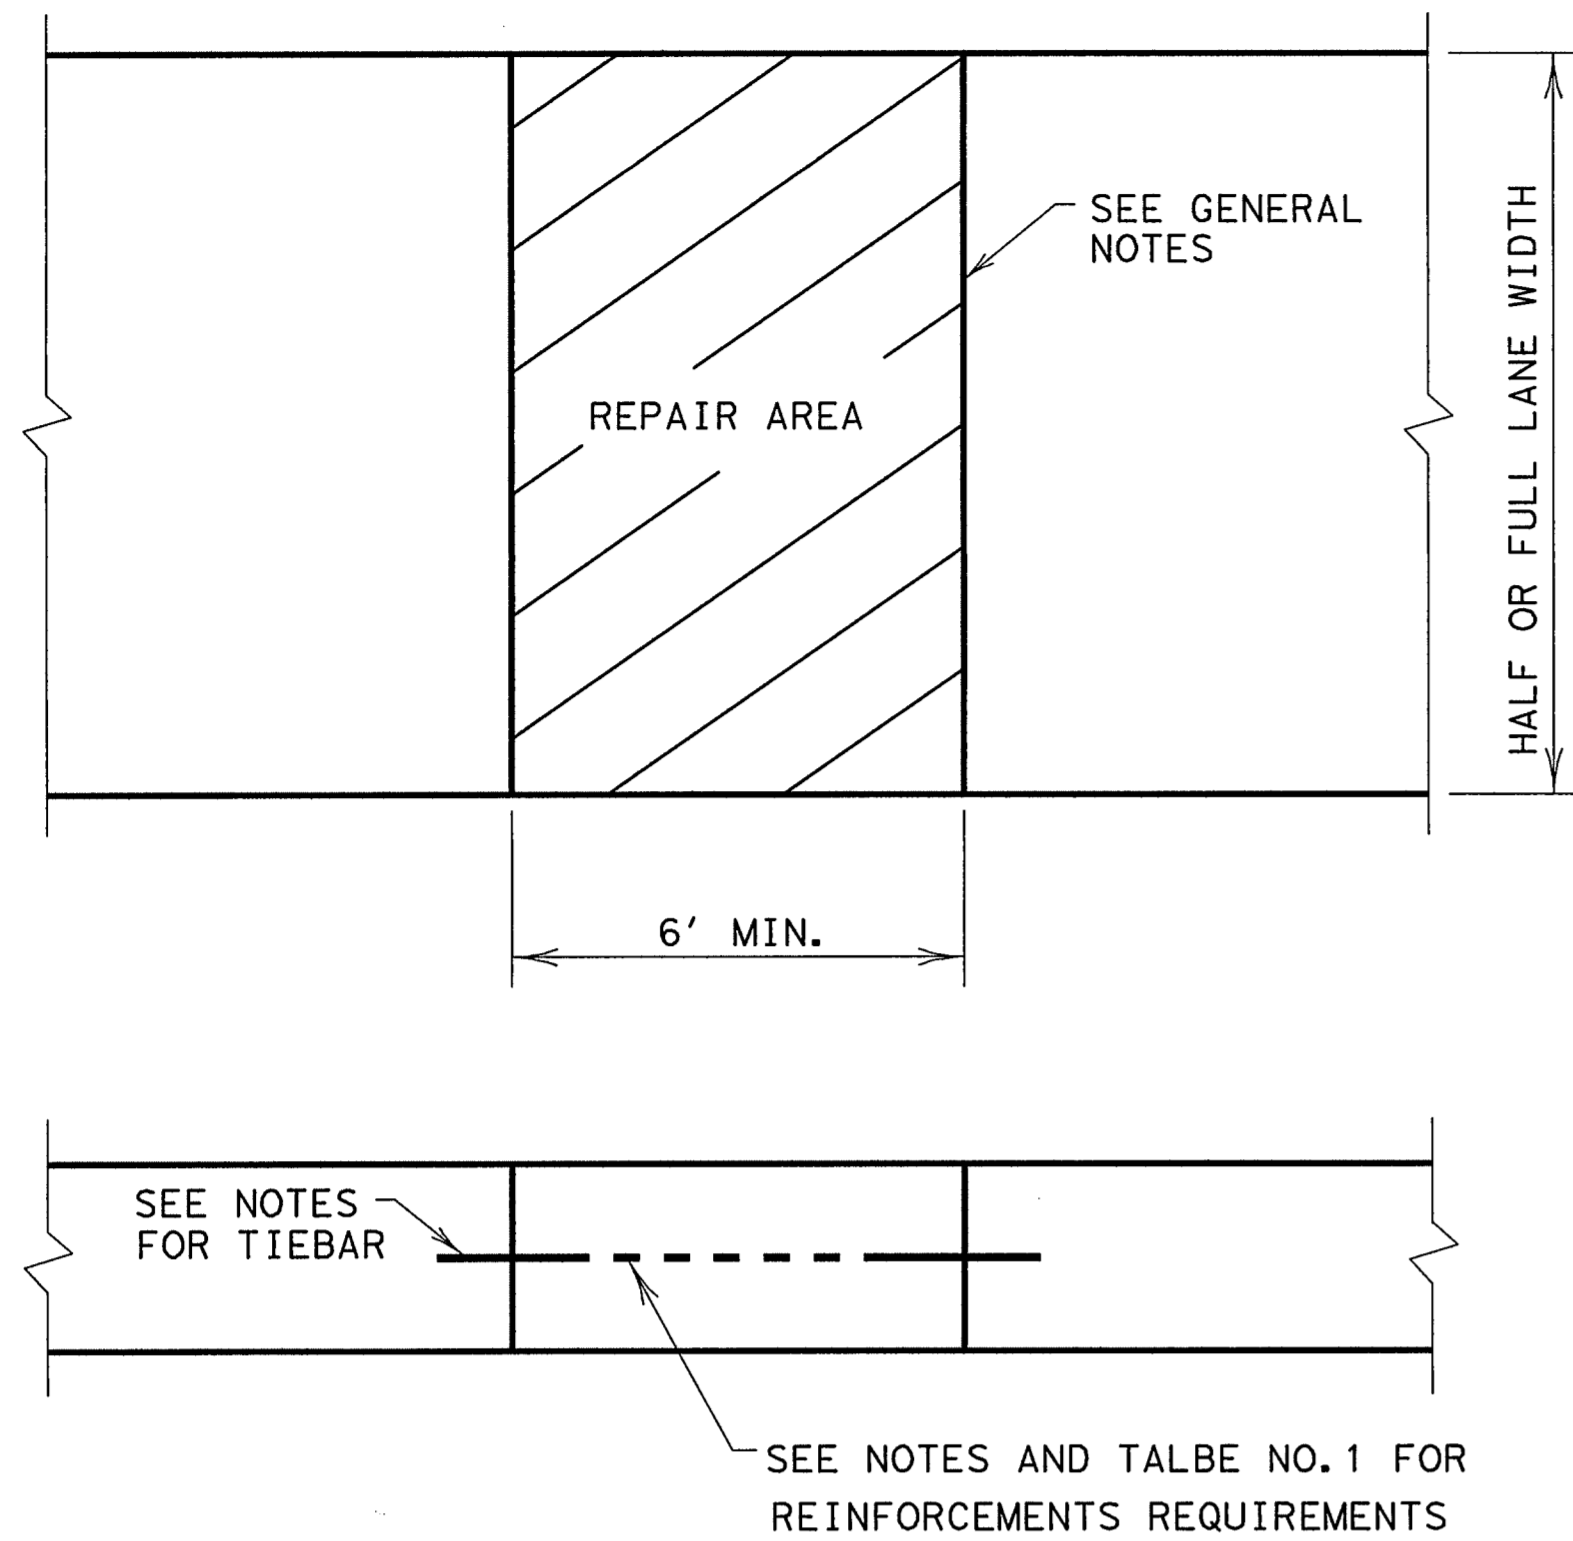

FULL DEPTH TRANSVERSE JOINT REPAIR

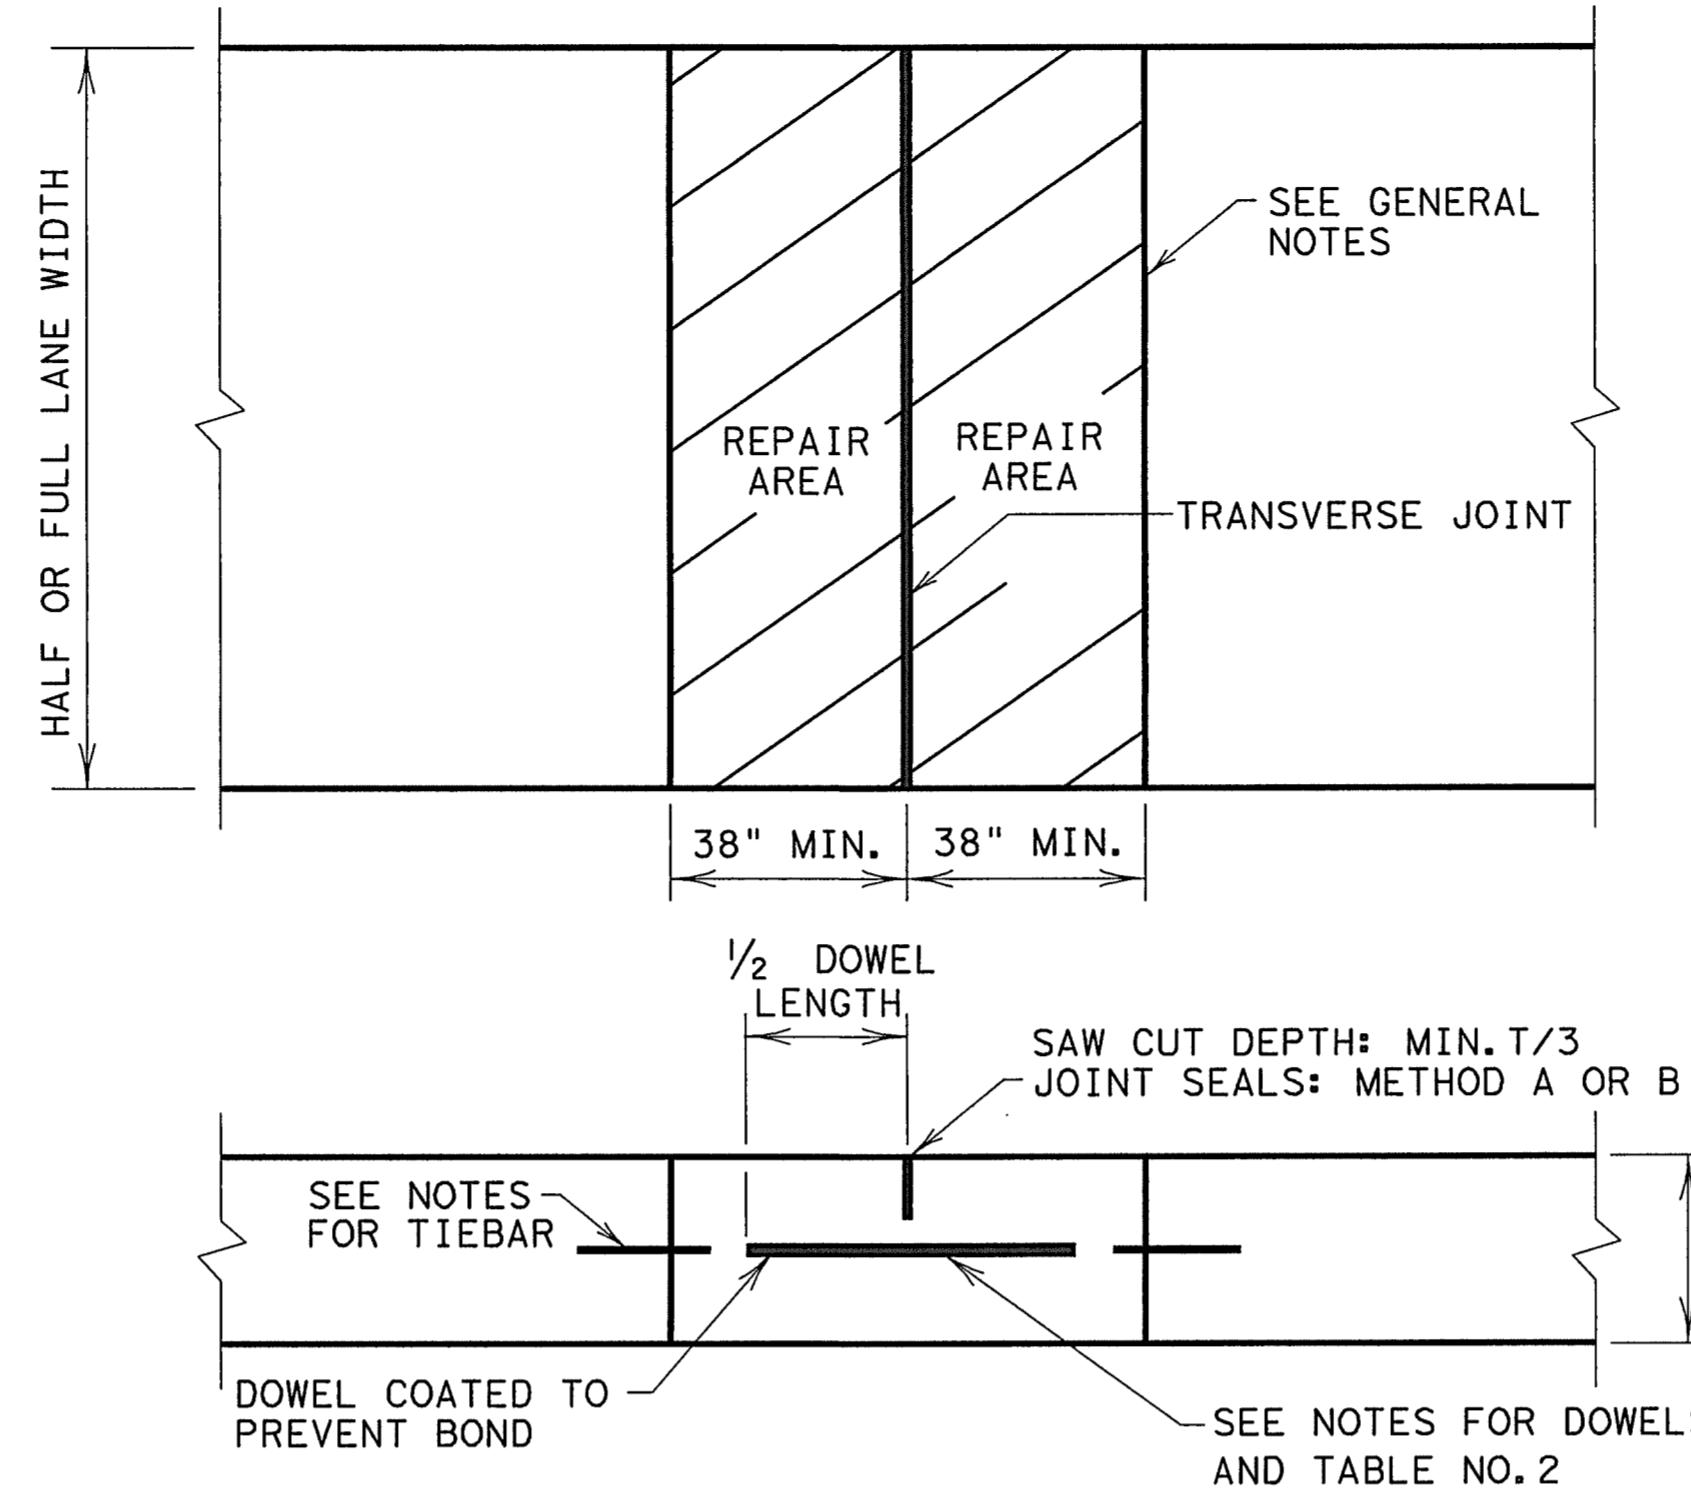

TRANSVERSE CONTRACTION JOINT

GENERAL NOTES:

- ITEM 361, "FULL-DEPTH REPAIR OF CONCRETE PAVEMENT," SHALL GOVERN FOR THIS WORK. THE FOLLOWING SPECIFICATIONS ARE REFERENCED IN ITEM 361.
 - * ITEM 360, " CONCRETE PAVEMENT "
 - * ITEM 421, " HYDRAULIC CEMENT CONCRETE "
 - * ITEM 438, " CLEANING AND SEALING JOINTS AND CRACKS (RIGID PAVEMENT AND BRIDGE DECKS) "
 - * ITEM 440, " REINFORCING STEEL "
 - * DMS-4650, " HYDRAULIC CEMENT CONCRETE CURING MATERIALS AND EVAPORATION RETARDANTS "
 - * DMS-6100, " EPOXIES AND ADHESIVES "
 - * DMS-6310, " JOINT SEALANTS AND FILLERS "
- FULL DEPTH SAW CUTS SHALL BE MADE AROUND THE PERIMETER OF THE AREA TO BE REPAIRED. THE CUT SHALL BE MADE AT A RIGHT ANGLE TO THE PAVEMENT EDGE AND TO THE CENTER LINE OF THE PAVEMENT.
- LONGITUDINAL FULL DEPTH SAW CUTS SHALL BE AT EXISTING LONGITUDINAL JOINTS.
- ADDITIONAL SAW CUTS MAY BE REQUIRED WITHIN THE AREA OF THE REPAIR TO FACILITATE REMOVAL OF THE CONCRETE OR TO ALLEVIATE BINDING OF THE FULL DEPTH SAW CUT AT THE REPAIR EDGE.
- THE SAW CUTS WHICH EXTEND OUTSIDE THE AREA OF THE REPAIR WILL BE CLEANED AND FILLED WITH A GROUT APPROVED BY THE ENGINEER.
- EXISTING LONGITUDINAL AND TRANSVERSE JOINTS REMOVED DUE TO REPAIR OPERATION SHOULD BE RESTORED IN ACCORDANCE WITH STANDARD SHEET "CONCRETE PAVING DETAILS, JOINT SEALS."

REINFORCEMENTS REQUIREMENTS

REINFORCING STEEL SHALL BE #6 DEFORMED STEEL BARS CONFORMING TO ASTM A 615 (GRADE 60) OR ASTM A 996 (GRADE 60).

- THE STEEL SPACING FOR CONTINUOUSLY REINFORCED CONCRETE PAVEMENT (CRCP) AND JOINTED REINFORCED CONCRETE PAVEMENT (JRCP) SHALL BE REINFORCED AS SHOWN IN TABLE NO. 1.
- REINFORCING BARS SHALL BE PLACED IN ONE LAYER AND SHALL BE TIED TO THE TIEBARS.
- THE LENGTH OF THE REINFORCING BAR SHALL BE THE LENGTH OR WIDTH OF THE REPAIR AREA MINUS 2 INCHES. THE END OF THE BAR SHALL BE PLACED WITHIN 1 INCH FROM THE REPAIR EDGE.

TIEBARS FOR REPAIR AREAS

- TIEBARS SHALL BE PLACED AT APPROXIMATELY THE MID-DEPTH OF SLAB. THE BOTTOM OF THE HOLE DRILLED FOR THE LONGITUDINAL BARS SHALL BE AT MID-DEPTH AND THE TOP OF THE HOLES DRILLED FOR THE TRANSVERSE BARS SHALL BE AT MID-DEPTH. MID-DEPTH WILL BE ESTABLISHED BY MEASURING FROM THE TOP OF THE SLAB DOWN. THE THICKNESS OF THE CONCRETE SLAB WILL BE DEFINED BY THE PLANS OR THE ENGINEER.
- THE BAR SIZE AND SPACING OF TIEBARS ARE SHOWN IN TABLE NO. 1.
- THE MINIMUM LENGTH OF TIEBARS EXTENDED INTO THE REPAIR AREA SHOULD BE 25 INCHES FOR A #6 BAR.
- THE TIEBAR SHALL BE GROUTED INTO THE EXISTING CONCRETE A MINIMUM OF 12 INCHES. BEFORE REPAIR WORK, DEMONSTRATE THAT THE BOND STRENGTH OF THE EPOXY-GROUTED TIEBARS MEETS THE REQUIREMENTS OF PULL-OUT TEST SPECIFIED IN ITEM 361.
- MULTIPLE PIECE TIEBARS SHALL BE USED WHEN THE REPAIR AREA MUST BE PLACED IN TWO STAGES DUE TO SEQUENCE OF CONSTRUCTION.

DOWELS FOR TRANSVERSE JOINT REPAIRS

- SMOOTH DOWEL BARS SHALL BE DELIVERED TO THE JOBS SITE IN PREFABRICATED DOWEL ASSEMBLIES. THE ENTIRE DOWEL BAR SHALL BE COATED WITH A MATERIAL WHICH WILL PREVENT BONDING TO THE CONCRETE.
- THE SIZE AND SPACING OF DOWEL BARS SHALL BE AS SHOWN IN TABLE NO. 2.
- PLACEMENT OF TIEBARS AND OTHER REINFORCING STEEL SHALL BE STOPPED APPROXIMATELY 4" FROM THE DOWEL BAR ASSEMBLY.
- DOWEL BAR PLACEMENT SHALL MEET THE REQUIREMENTS OF ITEM 360, "CONCRETE PAVEMENT."

TABLE NO. 2 DOWELS (SMOOTH BARS)

| PAVEMENT THICKNESS (INCHES) | SIZE AND DIA. | LENGTH (INCHES) | SPACING (INCHES) |
|-----------------------------|-----------------|-----------------|------------------|
| 8 | #8 (1 IN.) | 18 | 12 |
| 9 | #9 (1 1/8 IN.) | | |
| ≥10 | #10 (1 1/4 IN.) | | |

TABLE NO. 1 STEEL BARS SIZE AND SPACING

| TYPE OF REINFORCEMENTS | TYPE PAVEMENT | PAVEMENT THICKNESS (INCHES) | TIEBARS | | REGULAR REBARS | | ALL BARS FIRST & LAST SPACING AT END OR SIDE (INCHES) |
|------------------------|---------------|-----------------------------|--------------------|----------------------|--------------------|------------------|--|
| | | | SIZE BAR (BAR NO.) | BAR SPACING (INCHES) | SIZE BAR (BAR NO.) | SPACING (INCHES) | |
| TRANSVERSE BARS | CRCP | ALL | #6 | 24 | #6 | 24 | 12 |
| | JRCP (CPCD) | ALL | #6 | 24 | NONE | NONE | 12 |
| LONGITUDINAL BARS | CRCP | 8 | #6 | 9 | #6 | 9 | 12 |
| | | 9 | #6 | 8 | #6 | 8 | 12 |
| | | 10 | #6 | 7 | #6 | 7 | 12 |
| | | 11 | #6 | 6.5 | #6 | 6.5 | 12 |
| | ≥ 12 | #6 | 6 | #6 | 6 | 12 | |
| | JRCP (CPCD) | ALL | #6 | 12 | #6 | 24 | 12 |
| | JCP (CPCD) | ALL | #6 | 12 | NONE | NONE | 12 |



FULL DEPTH REPAIR FOR CONCRETE PAVEMENT

FDR (CP) -05

| | | | | |
|------------------------|-----------|--------|--------|-----------|
| FILE: fdrpc05.dgn | DN: TxDOT | CK: LL | DW: HC | CK: |
| © TxDOT September 1994 | CONT | SECT | JOB | HIGHWAY |
| REVISIONS | | | | |
| DIST | COUNTY | | | SHEET NO. |